



INTERNATIONAL TELECOMMUNICATION UNION

ITU-T

TELECOMMUNICATION
STANDARDIZATION SECTOR
OF ITU

G.653

(04/97)

SERIES G: TRANSMISSION SYSTEMS AND MEDIA,
DIGITAL SYSTEMS AND NETWORKS

Transmission media characteristics – Optical fibre cables

Characteristics of a dispersion-shifted single-mode optical fibre cable

ITU-T Recommendation G.653

(Previously CCITT Recommendation)

ITU-T G-SERIES RECOMMENDATIONS
TRANSMISSION SYSTEMS AND MEDIA, DIGITAL SYSTEMS AND NETWORKS

INTERNATIONAL TELEPHONE CONNECTIONS AND CIRCUITS	G.100–G.199
INTERNATIONAL ANALOGUE CARRIER SYSTEM	
GENERAL CHARACTERISTICS COMMON TO ALL ANALOGUE CARRIER-TRANSMISSION SYSTEMS	G.200–G.299
INDIVIDUAL CHARACTERISTICS OF INTERNATIONAL CARRIER TELEPHONE SYSTEMS ON METALLIC LINES	G.300–G.399
GENERAL CHARACTERISTICS OF INTERNATIONAL CARRIER TELEPHONE SYSTEMS ON RADIO-RELAY OR SATELLITE LINKS AND INTERCONNECTION WITH METALLIC LINES	G.400–G.449
COORDINATION OF RADIOTELEPHONY AND LINE TELEPHONY	G.450–G.499
TRANSMISSION MEDIA CHARACTERISTICS	
General	G.600–G.609
Symmetric cable pairs	G.610–G.619
Land coaxial cable pairs	G.620–G.629
Submarine cables	G.630–G.649
Optical fibre cables	G.650–G.659
Characteristics of optical components and sub-systems	G.660–G.699
DIGITAL TRANSMISSION SYSTEMS	
TERMINAL EQUIPMENTS	G.700–G.799
DIGITAL NETWORKS	G.800–G.899
DIGITAL SECTIONS AND DIGITAL LINE SYSTEM	G.900–G.999

For further details, please refer to ITU-T List of Recommendations.

ITU-T RECOMMENDATION G.653

CHARACTERISTICS OF A DISPERSION-SHIFTED SINGLE-MODE OPTICAL FIBRE CABLE

Summary

This Recommendation covers the geometrical and transmissive properties of dispersion-shifted single-mode optical fibres and cables. The chromatic dispersion minimum for this fibre type is shifted into the 1550 nm wavelength region. Definitions and test methods are contained in a separate Recommendation G.650.

Source

ITU-T Recommendation G.653 was revised by ITU-T Study Group 15 (1997-2000) and was approved under the WTSC Resolution No. 1 procedure on the 8th of April 1997.

FOREWORD

ITU (International Telecommunication Union) is the United Nations Specialized Agency in the field of telecommunications. The ITU Telecommunication Standardization Sector (ITU-T) is a permanent organ of the ITU. The ITU-T is responsible for studying technical, operating and tariff questions and issuing Recommendations on them with a view to standardizing telecommunications on a worldwide basis.

The World Telecommunication Standardization Conference (WTSC), which meets every four years, establishes the topics for study by the ITU-T Study Groups which, in their turn, produce Recommendations on these topics.

The approval of Recommendations by the Members of the ITU-T is covered by the procedure laid down in WTSC Resolution No. 1.

In some areas of information technology which fall within ITU-T's purview, the necessary standards are prepared on a collaborative basis with ISO and IEC.

NOTE

In this Recommendation, the expression "Administration" is used for conciseness to indicate both a telecommunication administration and a recognized operating agency.

INTELLECTUAL PROPERTY RIGHTS

The ITU draws attention to the possibility that the practice or implementation of this Recommendation may involve the use of a claimed Intellectual Property Right. The ITU takes no position concerning the evidence, validity or applicability of claimed Intellectual Property Rights, whether asserted by ITU members or others outside of the Recommendation development process.

As of the date of approval of this Recommendation, the ITU had/had not received notice of intellectual property, protected by patents, which may be required to implement this Recommendation. However, implementors are cautioned that this may not represent the latest information and are therefore strongly urged to consult the TSB patent database.

© ITU 1997

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the ITU.

CONTENTS

	Page
1 Scope.....	1
2 References.....	1
3 Terminology.....	2
4 Abbreviations.....	2
5 Fibre characteristics	2
5.1 Mode field diameter.....	2
5.2 Cladding diameter.....	2
5.3 Mode field concentricity error	2
5.4 Non-circularity.....	2
5.4.1 Mode field non-circularity.....	2
5.4.2 Cladding non-circularity.....	3
5.5 Cut-off wavelength	3
5.6 1550 nm bend performance	3
5.7 Material properties of the fibre	4
5.7.1 Fibre materials	4
5.7.2 Protective materials	4
5.7.3 Proofstress level.....	4
5.8 Refractive index profile	4
5.9 Longitudinal uniformity.....	4
6 Factory length specifications	4
6.1 Attenuation coefficient.....	4
6.2 Chromatic dispersion coefficient.....	5
6.3 Polarization mode dispersion coefficient.....	6
7 Elementary cable sections.....	6
7.1 Attenuation.....	6
7.2 Chromatic dispersion	7

Recommendation G.653

CHARACTERISTICS OF A DISPERSION-SHIFTED SINGLE-MODE OPTICAL FIBRE CABLE

(revised in 1997)

1 Scope

This Recommendation describes a dispersion-shifted single-mode fibre which has a nominal zero-dispersion wavelength close to 1550 nm, and a dispersion coefficient which is monotonically increasing with wavelength. This fibre is optimized for use at wavelengths in the region between 1550 nm and 1600 nm, but may also be used at around 1310 nm subject to the constraints outlined in this Recommendation.

Its geometrical, optical, transmission and mechanical parameters are described below.

The meaning of the terms used in this Recommendation and the guidelines to be followed in the measurements to verify the various characteristics are given in Recommendation G.650. The characteristic of this fibre, including the definitions of the relevant parameters, their test methods and relevant values, will be refined as studies and experience progress.

2 References

The following ITU-T Recommendations and other references contain provisions which, through reference in this text, constitute provisions of this Recommendation. At the time of publication, the editions indicated were valid. All Recommendations and other references are subject to revision; all users of this Recommendation are therefore encouraged to investigate the possibility of applying the most recent edition of the Recommendations and other references listed below. A list of the currently valid ITU-T Recommendations is regularly published.

- ITU-T Recommendation G.650 (1997), *Definition and test methods for the relevant parameters of single-mode fibres*.
- ITU-T Recommendation G.652 (1997), *Characteristics of a single-mode optical fibre cable*.
- ITU-T Recommendation G.654 (1997), *Characteristics of a cut-off shifted single-mode optical fibre cable*.
- ITU-T Recommendation G.655 (1996), *Characteristics of a non-zero-dispersion shifted single-mode optical fibre cable*.
- ITU-T Recommendation G.955 (1996), *Digital line systems based on the 1544 kbit/s and the 2048 kbit/s hierarchy on optical fibre cables*.
- ITU-T Recommendation G.957 (1996), *Optical interfaces for equipments and systems relating to the synchronous digital hierarchy*.
- ITU-T Recommendation G.681 (1996), *Functional characteristics of interoffice and long-haul line systems using optical amplifiers, including optical multiplexing*.
- ITU-T Recommendation G.663 (1996), *Application related aspects of optical fibre amplifier devices and sub-systems*.
- IEC Publication 793-2, Part 2 (1992), *Optical fibres – Part 2: Product specifications*.

3 Terminology

For the purposes of this Recommendation, the definitions given in Recommendation G.650 apply.

4 Abbreviations

This Recommendation uses the following abbreviations:

GPa GigaPascals

SDH Synchronous Digital Hierarchy

WDM Wavelength Division Multiplexing

5 Fibre characteristics

Only those characteristics of the fibre providing a minimum essential design framework for fibre manufacture are recommended in this clause. Of these, the cabled fibre cut-off wavelength may be significantly affected by cable manufacture or installation. Otherwise, the recommended characteristics will apply equally to individual fibres, fibres incorporated into a cable wound on a drum, and fibres in an installed cable.

This Recommendation applies to fibres having a nominally circular mode field.

5.1 Mode field diameter

The nominal value of the mode field diameter at 1550 nm shall lie within the range of 7.8 to 8.5 μm . The mode field diameter deviation should not exceed the limits of $\pm 10\%$ of the nominal value.

NOTE 1 – The choice of a specific value within the above range is not necessarily associated with a specific fibre design.

NOTE 2 – It should be noted that the fibre performance required for any given application is a function of essential fibre and systems parameters, i.e. mode field diameters, cut-off wavelength, chromatic dispersion, system operating wavelength, and bit rate/frequency of operation, and not primarily of the fibre design.

5.2 Cladding diameter

The recommended nominal value of the cladding diameter is 125 μm . The cladding deviation should not exceed the limits of $\pm 2 \mu\text{m}$.

For some particular jointing techniques and joint loss requirements, other tolerances may be appropriate.

5.3 Mode field concentricity error

The recommended mode field concentricity error at 1550 nm should not exceed 1 μm .

NOTE – For some particular jointing techniques and joint loss requirements, tolerances up to 3 μm may be appropriate.

5.4 Non-circularity

5.4.1 Mode field non-circularity

In practice, the mode field non-circularity of fibres having nominally circular mode fields is found to be sufficiently low that propagation and jointing are not affected. It is therefore not considered necessary to recommend a particular value for the mode field non-circularity. It is not normally necessary to measure the mode field non-circularity for acceptance purposes.

5.4.2 Cladding non-circularity

The cladding non-circularity should be less than 2%. For some particular jointing techniques and joint loss requirements, other tolerances may be appropriate.

5.5 Cut-off wavelength

Three useful types of cut-off wavelength can be distinguished:

- a) cable cut-off wavelength λ_{cc} ;
- b) fibre cut-off wavelength λ_c ;
- c) jumper cable cut-off wavelength λ_{cj} .

The correlation of the measured values of λ_c , λ_{cc} and λ_{cj} depends on the specific fibre and cable design and the test conditions. While in general $\lambda_{cc} < \lambda_{cj} < \lambda_c$, a general quantitative relationship cannot easily be established. The importance of ensuring single-mode transmission in the minimum cable length between joints at the minimum system operating wavelength is paramount. This may be performed by recommending the maximum cable cut-off wavelength λ_{cc} of a cabled single-mode fibre to be 1270 nm, a maximum jumper cable cut-off wavelength λ_{cj} to be 1270 nm, or recommending a maximum fibre cut-off wavelength, λ_c .

NOTE – The above recommendation is not sufficient to ensure 1310 nm region single-mode operation in any possible combination of system operating wavelength, cable length and cable deployment conditions. Suitable limits on λ_c or λ_{cc} should be set in case 1310 nm region operation is foreseen, with particular attention to prevent modal noise effects in minimum cable lengths between repair joints and cable jumpers.

5.6 1550 nm bend performance

The loss increase for 100 turns of fibre, loosely wound with 37.5 mm radius and measured at 1550 nm, shall be less than 0.5 dB.

For SDH and WDM applications, the fibre may be used at wavelengths exceeding 1550 nm. The 1.0 dB maximum loss shall apply at the maximum wavelength of anticipated use (which would be ≤ 1580 nm). The loss at the maximum wavelength may be projected from a loss measurement at 1550 nm, using either spectral loss modelling or a statistical database for that particular fibre design. Alternatively, a qualification test at the longer wavelength may be performed.

NOTE 1 – A qualification test may be sufficient to ensure that this requirement is being met.

NOTE 2 – The above value of 100 turns corresponds to the approximate number of turns deployed in all splice cases of a typical repeater span. The radius of 37.5 mm is equivalent to the minimum bend-radius widely accepted for long-term deployment of fibres in practical systems installations to avoid static-fatigue failure.

NOTE 3 – If for practical reasons fewer than 100 turns are chosen to implement this 37.5 mm test, it is suggested that not less than 40 turns, and a proportionately smaller loss increase be used.

NOTE 4 – If bending radii smaller than 37.5 mm are planned to be used in splice cases or elsewhere in the system (for example, $R = 30$ mm), it is suggested that the same loss value of 0.5 dB shall apply to 100 turns of fibre deployed with this smaller radius.

NOTE 5 – The 1550 nm bend-loss recommendation relates to the deployment of fibres in practical single-mode fibre installations. The influence of the stranding-related bending radii of cabled single-mode fibres on the loss performance is included in the loss specification of the cabled fibre.

NOTE 6 – In the event that routine tests are required a small diameter loop with one or several turns can be used instead of the 100-turn test, for accuracy and measurement ease of the 1550 nm bend sensitivity. In this case, the loop diameter, number of turns, and the maximum permissible bend loss for the several-turn test should be chosen, so as to correlate with the 0.5 dB loss recommendation of the 37.5 mm radius 100-turn functional test.

5.7 Material properties of the fibre

5.7.1 Fibre materials

The substances of which the fibres are made should be indicated.

NOTE – Care may be needed in fusion splicing fibres of different substances. Provisional results indicate that adequate splice loss and strength can be achieved when splicing different high-silica fibres.

5.7.2 Protective materials

The physical and chemical properties of the material used for the fibre primary coating, and the best way of removing it (if necessary) should be indicated. In the case of single jacketed fibre, similar indications shall be given.

5.7.3 Proofstress level

The specified proofstress σ_p shall be at least 0.35 GPa, which corresponds to a proofstrain of approximately 0.5%. Proofstress is often specified as 0.69 GPa.

NOTE – The definitions of the mechanical parameters are contained in 1.2/G.650 and 2.6/G.650.

5.8 Refractive index profile

The refractive index profile of the fibre does not generally need to be known; if one wishes to measure it, the reference test method in Recommendation G.651 may be used.

5.9 Longitudinal uniformity

Under study.

6 Factory length specifications

Since the geometrical and optical characteristics of fibres given in clause 5 are barely affected by the cabling process, this clause will give recommendations mainly relevant to transmission characteristics of cabled factory lengths.

Environment and test conditions are paramount and are described in the guidelines for test methods.

6.1 Attenuation coefficient

Optical fibre cables covered by this Recommendation generally have attenuation coefficients in the 1550 nm region below 0.35 dB/km. When they are intended for use in the 1300 nm region, their attenuation coefficient in that region is generally below 0.55 dB/km.

NOTE – The lowest values depend on the fabrication process, fibre composition and design, and cable design. Values in the range of 0.19-0.25 dB/km in the 1550 nm region have been achieved.

6.2 Chromatic dispersion coefficient

The following equation specifies the chromatic dispersion $D(\lambda)$, in ps/(nm · km), as:

$$D(\lambda) = (\lambda - \lambda_0)S_0$$

where λ is the wavelength of interest, in nm, λ_0 is the zero-dispersion wavelength in nm, and S_0 is the zero-dispersion slope in ps/(nm² · km). The slope S_0 , is specified by its maximum value: $S_0 < S_{0\max}$. The zero dispersion wavelength, λ_0 , is specified by the nominal value of 1550 and its maximum tolerance, $\Delta\lambda_{0\max}$, above and below 1550 nm (considered symmetrical):

$$1550 - \Delta\lambda_{0\max} < \lambda_0 < 1550 + \Delta\lambda_{0\max}$$


In addition, the maximum absolute value of the dispersion coefficient, in D_{\max} , in ps/(nm · km), is specified over the specified window width, $\Delta\lambda_w$, in nm, above and below 1550 nm. Then:

$$\begin{aligned} |D(\lambda)| &< D_{\max} \\ \text{for } 1550 - \Delta\lambda_w &< \lambda < 1550 + \Delta\lambda_w \end{aligned}$$

Users operating with a transmitter central wavelength separated from 1550 nm (either above or below) by $\Delta\lambda_t$ in nm, may calculate the maximum absolute value of the dispersion coefficient as:

$$\begin{aligned} D_m(\Delta\lambda_t) &= D_{\max} \frac{\Delta\lambda_t + \Delta\lambda_{0\max}}{\Delta\lambda_w + \Delta\lambda_{0\max}} \\ &\text{for } 0 \leq \Delta\lambda_t \leq \Delta\lambda_w \text{ and} \\ D_m(\Delta\lambda_t) &= D_{\max} + S_{0\max}(\Delta\lambda_t - \Delta\lambda_w) \\ &\text{for } \Delta\lambda_w \leq \Delta\lambda_t \leq 50 \text{ nm} \end{aligned}$$

where $D_{\max} = D_m(\Delta\lambda_w)$. Figure 1 schematically illustrates the specification:

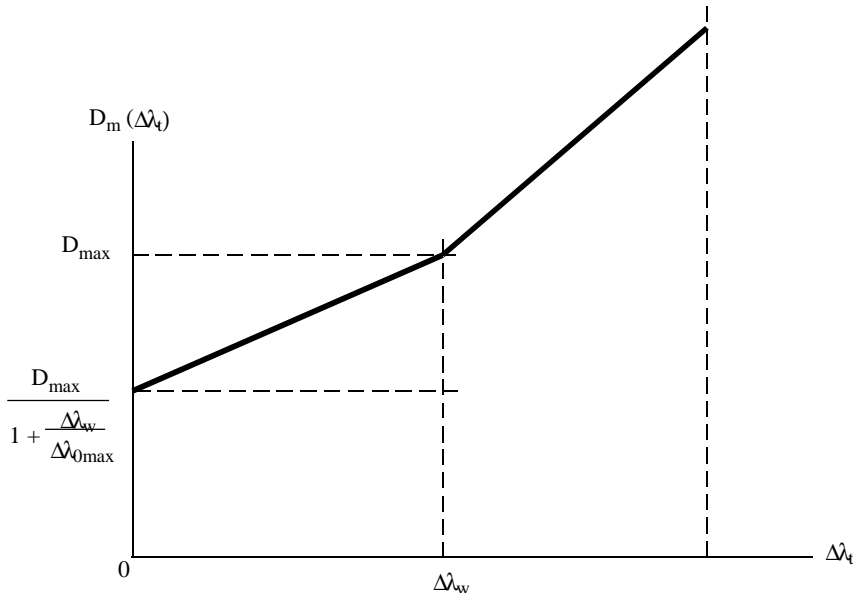

T1507800-92

Figure 1/G.653 – Maximum absolute value of the dispersion coefficient

The specification of the dispersion coefficient for this Recommendation is as follows:

$$\Delta \lambda_{0\max} \leq 50 \text{ nm}$$

$$S_{0\max} \leq 0.085 \text{ ps}/(\text{nm}^2 \cdot \text{km})$$

$$D_{\max} = 3.5 \text{ ps}/(\text{nm} \cdot \text{km}) \text{ between } 1525 \text{ and } 1575 \text{ nm}$$

$$\Delta \lambda_w = 25 \text{ nm}$$

NOTE 1 – The values above are provisionally specified in order to give guidance to fibre and system designers. Further study and trade-offs between $\Delta \lambda_{0\max}$ and $S_{0\max}$ may be needed in the future to improve the fibre dispersion performances in the working wavelength window.

NOTE 2 – It is not necessary to measure the chromatic dispersion coefficient on a routine basis.

6.3 Polarization mode dispersion coefficient

Under study.

NOTE – Optical fibre cables covered by this Recommendation generally have a polarization mode dispersion coefficient below $0.5 \text{ ps}/\text{km}^{1/2}$. This corresponds to a PMD-limited transmission distance of about 400 km for STM-64 systems.

Systems without lower bit rate distance products can tolerate higher values of PMD coefficient without impairment.

7 Elementary cable sections

An elementary cable section usually includes a number of spliced factory lengths. The requirements for factory lengths are given in clause 6. The transmission parameters for elementary cable sections must take into account not only the performance of the individual cable lengths, but also, amongst other factors, such things as splice losses and connector losses (if applicable).

In addition, the transmission characteristics of the factory length fibres as well as such items as splices and connectors, etc. will all have a certain probability distribution which often needs to be taken into account if the most economic designs are to be obtained. The following subclauses should be read with this statistical nature of the various parameters in mind.

7.1 Attenuation

The attenuation A of an elementary cable section is given by:

$$A = \sum_{n=1}^m \alpha_n \cdot L_n + \alpha_s \cdot \chi + \alpha_c \cdot y$$

where:

α_n = attenuation coefficient of n th fibre in elementary cable section;

L_n = length of n th fibre;

m = total number of concatenated fibres in elementary cable section;

α_s = mean splice loss;

χ = number of splices in elementary cable section;

α_c = mean loss of line connectors;

y = number of line connectors in elementary cable section (if provided).

A suitable allowance should be allocated for a suitable cable margin for future modifications of cable configurations (additional splices, extra cable lengths, ageing effects, temperature variations, etc.). The above equation does not include the loss of equipment connectors.

The mean loss is used for the loss of splices and connectors. The attenuation budget used in designing an actual system should account for the statistical variations in these parameters.

7.2 Chromatic dispersion

The chromatic dispersion in ps can be calculated from the chromatic dispersion coefficients of the factory lengths, assuming a linear dependence on length, and with due regard for the signs of the coefficients and system source characteristics (see 6.2).

ITU-T RECOMMENDATIONS SERIES

Series A	Organization of the work of the ITU-T
Series B	Means of expression: definitions, symbols, classification
Series C	General telecommunication statistics
Series D	General tariff principles
Series E	Overall network operation, telephone service, service operation and human factors
Series F	Non-telephone telecommunication services
Series G	Transmission systems and media, digital systems and networks
Series H	Audiovisual and multimedia systems
Series I	Integrated services digital network
Series J	Transmission of television, sound programme and other multimedia signals
Series K	Protection against interference
Series L	Construction, installation and protection of cables and other elements of outside plant
Series M	TMN and network maintenance: international transmission systems, telephone circuits, telegraphy, facsimile and leased circuits
Series N	Maintenance: international sound programme and television transmission circuits
Series O	Specifications of measuring equipment
Series P	Telephone transmission quality, telephone installations, local line networks
Series Q	Switching and signalling
Series R	Telegraph transmission
Series S	Telegraph services terminal equipment
Series T	Terminals for telematic services
Series U	Telegraph switching
Series V	Data communication over the telephone network
Series X	Data networks and open system communication
Series Z	Programming languages